



## NRC Publications Archive Archives des publications du CNRC

### **Structural and sintering characteristics of the La<sub>2</sub>Ni<sub>1-x</sub>CoxO<sub>4</sub>+() series** Amow, G.; Whitfield, P.S.; Davidson, I.J.; Hammond, R. P.; Munnings, C. N.; Skinner, S. J.

This publication could be one of several versions: author's original, accepted manuscript or the publisher's version. /  
La version de cette publication peut être l'une des suivantes : la version prépublication de l'auteur, la version  
acceptée du manuscrit ou la version de l'éditeur.

For the publisher's version, please access the DOI link below. / Pour consulter la version de l'éditeur, utilisez le lien  
DOI ci-dessous.

#### **Publisher's version / Version de l'éditeur:**

<https://doi.org/10.1016/j.ceramint.2003.12.164>

*Ceramics International*, 30, May 7, pp. 1635-1639, 2004

#### **NRC Publications Record / Notice d'Archives des publications de CNRC:**

<https://nrc-publications.canada.ca/eng/view/object/?id=feed36e4-af93-411c-a635-fbfee560f687>

<https://publications-cnrc.canada.ca/fra/voir/objet/?id=feed36e4-af93-411c-a635-fbfee560f687>

Access and use of this website and the material on it are subject to the Terms and Conditions set forth at

<https://nrc-publications.canada.ca/eng/copyright>

READ THESE TERMS AND CONDITIONS CAREFULLY BEFORE USING THIS WEBSITE.

L'accès à ce site Web et l'utilisation de son contenu sont assujettis aux conditions présentées dans le site

<https://publications-cnrc.canada.ca/fra/droits>

LISEZ CES CONDITIONS ATTENTIVEMENT AVANT D'UTILISER CE SITE WEB.

#### **Questions?** Contact the NRC Publications Archive team at

PublicationsArchive-ArchivesPublications@nrc-cnrc.gc.ca. If you wish to email the authors directly, please see the  
first page of the publication for their contact information.

**Vous avez des questions?** Nous pouvons vous aider. Pour communiquer directement avec un auteur, consultez la  
première page de la revue dans laquelle son article a été publié afin de trouver ses coordonnées. Si vous n'arrivez  
pas à les repérer, communiquez avec nous à PublicationsArchive-ArchivesPublications@nrc-cnrc.gc.ca.



# Structural and sintering characteristics of the $\text{La}_2\text{Ni}_{1-x}\text{Co}_x\text{O}_{4+\delta}$ series

G. Amow<sup>a</sup>, P.S. Whitfield<sup>a,\*</sup>, I.J. Davidson<sup>a</sup>, R.P. Hammond<sup>b</sup>,  
C.N. Munnings<sup>c</sup>, S.J. Skinner<sup>c</sup>

<sup>a</sup> Institute for Chemical Process and Environmental Technology, National Research Council, Ottawa, Ontario, Canada

<sup>b</sup> Neutron Program for Materials Research, Chalk River Laboratories, Chalk River, Ontario, Canada

<sup>c</sup> Centre for Ion Conducting Membranes, Department of Materials, Imperial College London, London, UK

Received 1 December 2003; received in revised form 12 December 2003; accepted 22 December 2003

Available online 8 May 2004

## Abstract

The solid solution,  $\text{La}_2\text{Ni}_{1-x}\text{Co}_x\text{O}_{4+\delta}$  ( $0.00 \leq x \leq 1.00$ ), based on the  $\text{K}_2\text{NiF}_4$  structure was synthesised and studied for potential use as cathodes in solid-oxide fuel cells. A structural phase transition was observed with increasing cobalt substitution, between  $x = 0.50$  and  $0.60$  from tetragonal to orthorhombic symmetry. An apparent correlation between the area specific resistance and microstructural properties has been found for materials produced using both conventional and microwave heating. The difference in microstructure for samples prepared by these two techniques persists even after firing on CGO and LSGM pellets at  $950^\circ\text{C}$  in air for 2 weeks.

© 2004 Published by Elsevier Ltd and Techna Group S.r.l.

**Keywords:** A. Microwave processing; B. X-ray methods; E. Fuel cells

## 1. Introduction

Recent demands for environmental protection and fuel efficiency have encouraged much work in the field of alternative energy sources. Fuel cells form a large part of this effort, and solid oxide fuel cells (SOFCs) are particularly attractive for residential, commercial and distributed power use given their very high efficiency in combined heat and power operation. SOFCs currently operate at very high temperatures ( $\sim 900$ – $1000^\circ\text{C}$ ), and to reduce the production and operating costs while retaining reliability, it is desirable to reduce the operating temperature. This creates challenges for all components of the SOFC; the cathode, electrolyte, anode and interconnect.


This work is directed at developing new materials for use as SOFC cathodes. The current material of choice for this application is the perovskite  $\text{La}_{1-x}\text{Sr}_x\text{MnO}_{3-\delta}$ . However, cubic perovskite materials optimised to operate in the intermediate temperature range suffer from a number of problems, most notably chemical and mechanical instabilities, without a clear solution. Some previous studies have suggested that systems based on the layered  $\text{K}_2\text{NiF}_4$  structure (Fig. 1), such

as  $\text{La}_2\text{NiO}_{4+\delta}$  may offer alternatives, as it exhibits relatively high electronic conductivity and oxygen diffusivity at elevated temperatures [1,2]. The parent nickelate,  $\text{La}_2\text{NiO}_{4+\delta}$ , is made up of alternating  $\text{LaNiO}_3$  perovskite and  $\text{La}_2\text{O}_2$  rock salt layers. Significant excess oxygen,  $\delta$ , can be incorporated into the rock-salt layer as interstitial defects [3]. A series of structural changes from tetragonal to orthorhombic symmetry may be induced by varying the amount of excess oxygen in the rock-salt layer [3,4].

Previous studies have reported differences in microstructure when electroceramics have been prepared and/or sintered using microwave as opposed to conventional radiative heating [5,6]. Given the sensitivity of many material properties to microstructure, microwave heating is interesting as a possible route to novel microstructures. It has been reported that  $\text{La}_2\text{Ni}_{0.9}\text{Co}_{0.1}\text{O}_{4+\delta}$ , exhibited lower area-specific resistance (ASR) values for symmetrical cells based on ceria-doped gadolinia (CGO) when microwave heating was used [6]. The difference was ascribed to variations in the microstructure derived from the different firing techniques. This paper will present a summary of the structural changes in the system with increasing cobalt substitution. In addition, evidence to support the notion that the lowering of the ASR values is inherently associated with differences in microstructure with microwave heating will be presented.

\* Corresponding author.


E-mail address: pamela.whitfield@nrc.ca (P.S. Whitfield).

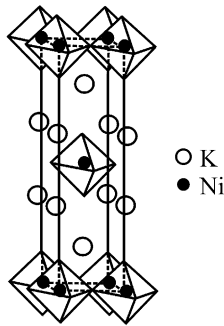Fig. 1. Ruddlesden-Popper  $K_2NiF_4$  structure.

## 2. Experimental

Samples of the  $La_2Ni_{1-x}Co_xO_{4+\delta}$  system ( $x = 0.00-1.00$ ,  $\Delta x = 0.10$ ) were prepared by the Pechini method [7] and is described elsewhere [8]. For the microwave-prepared samples, a modified Milestone furnace was used. For  $x = 0.00-0.20$ , the samples were prepared in air, whereas the remaining compositions for  $x \geq 0.30$  were prepared under argon.

Phase-purity determination was performed with a Cu  $K\alpha$  Bruker D8 parallel-beam X-ray diffractometer over  $10-100^\circ 2\theta$ , a step size of  $0.02^\circ$  and a count time of 10 s. Unit-cell parameter determination was performed using the program TOPAS [9]. Neutron data for structural analysis were collected at room temperature on the DUALSPEC C2 high-resolution powder diffractometer located at the Chalk River Laboratories, Ontario, Canada. Approximately 2–3 g of sample were loaded into vanadium cans for data collection. The wavelength used was  $\lambda = 1.3282(1) \text{ \AA}$ , and data collection covered a  $2\theta$  range of  $10-80^\circ$ ,  $\Delta 2\theta = 0.10^\circ$ . The patterns were refined using the GSAS package to perform Rietveld analysis [10].

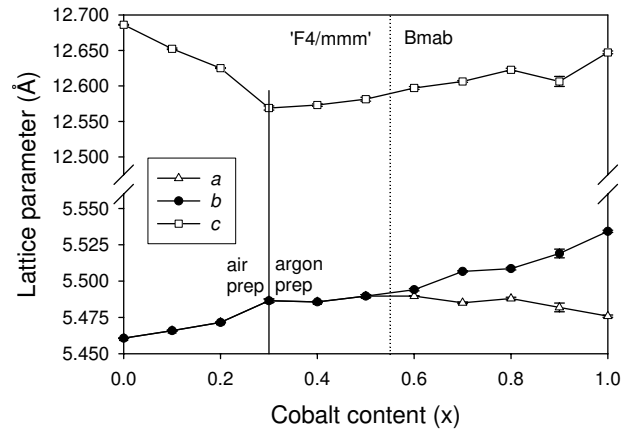Fig. 2. Plot of lattice parameters vs. cobalt content ( $x$ ).

Oxygen contents were determined by iodometry using potentiometric methods with a MetrOhm 751 GDP Titrimo autotitrator. These results were confirmed by thermogravimetric analysis obtained under reducing conditions in 10%  $H_2/90\% N_2$  atmosphere on a STA-780 Series, Stanton Redcroft Thermal Analyzer, heated at  $10^\circ C/min$  up to  $850^\circ C$ . All calculations were based on nominal cation contents.

Single phase  $La_2Ni_{0.9}Co_{0.1}O_{4+\delta}$  produced by conventional and microwave processing were deposited onto sintered electrolyte discs of  $Ce_{0.1}Gd_{0.9}O_{3-\delta}$  and  $La_{0.9}Sr_{0.1}Ga_{0.8}Mg_{0.2}O_3$  supplied by Praxair. The  $x = 0.10$  cathode material was mixed with terpinol to form an ink, which was subsequently painted onto both sides of the electrolyte and dried, followed by sintering in a conventional furnace in air at  $1000^\circ C$  for 2 h. The sintered bodies were examined using backscattering scanning electron microscopy with a Hitachi S-4700 FEG-SEM.

AC impedance spectroscopy measurements were carried out on a Solartron 1260 FRA over the frequency range

Table 1

Unit cell and atomic coordinates for  $La_2Ni_{0.50}Co_{0.50}O_{4.147}$  ( $F4/mmm$ ,  $a = 5.4904(3) \text{ \AA}$ ,  $c = 12.5694(8) \text{ \AA}$ ) and  $La_2Ni_{0.4}Co_{0.6}O_{4.093}$  ( $Bmab$ ,  $a = 5.4857(3) \text{ \AA}$ ,  $b = 5.5046(3) \text{ \AA}$ ,  $c = 12.5999(6) \text{ \AA}$ )

Atom	Mult	$x$	$y$	$z$	Occupancy	$U_{iso}$
La	8	0	0 <i>0.0014(18)</i>	0.3616(2) <i>0.3618(2)</i>	1	0.0065(8) <i>0.0064(6)</i>
Ni	4	0	0	0	0.499(14) <i>0.391(10)</i>	0.0026(15) <i>0.0033(12)</i>
Co					0.501(14) <i>0.609(10)</i>	0.0026(15) <i>0.0033(12)</i>
O(1)	8	0.25	0.25	0 <i>-0.0068(5)</i>	1	0.0069(10) <i>0.0053(7)</i>
O(2)	8	0	0 <i>-0.0214(5)</i>	0.1713(8) <i>0.1729(5)</i>	0.603(16) <i>0.697(14)</i>	0.0061(21) <i>0.0083(15)</i>
O(3)	8	0.25	0.25	0.25 <i>0.2366(47)</i>	0.083(7) <i>0.074(6)</i>	0.0061(21) <i>0.0083(15)</i>
O(4)	32 16	-0.0689(29) <i>0.057(4)</i>	-0.0689(29) <i>0.0766(51)</i>	0.1757(20) <i>0.1729(5)</i>	0.097(6) <i>0.138(10)</i>	0.0061(21) <i>0.0083(15)</i>

The data for the orthorhombic phase are in italics.


13 MHz to 0.01 Hz and a temperature range of 500–900 °C. This data was then normalised to give an area specific resistance for each of the symmetrical cells tested. Long-term stability was evaluated by firing the cathode-electrolyte pellets at 950 °C in air for 2 weeks.

### 3. Results and discussion


All of the materials prepared in this study were identified as single-phase by X-ray diffraction. As previously re-

ported, the oxygen excess,  $\delta$ , as determined by iodometric titration showed an apparent trend of increased  $\delta$  with cobalt content, regardless whether the samples were prepared in air or argon [8]. A decrease in  $\delta$  at  $x = 0.60$  indicated a possible structural phase transition. Initial structural investigations by X-ray diffraction (XRD) revealed two general structural types, tetragonal  $F4/mmm$  (non-standard setting of  $I4/mmm$ ) and orthorhombic  $Bmab$  with some ambiguity in the  $x = 0.50$  and  $0.60$  compositions.

The refined unit-cell parameters (Fig. 2) indicate a deviation from the expected tetragonal  $c/a$  ratio of 3.30 and

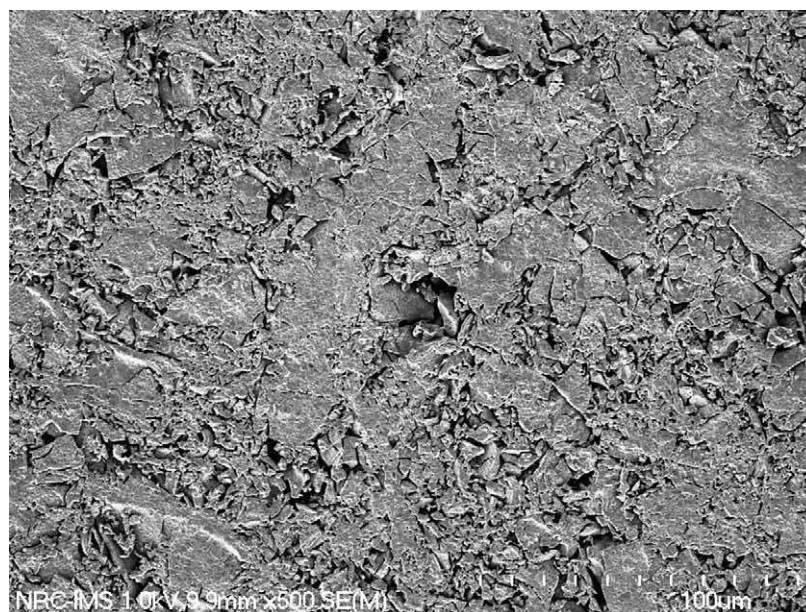

(a)

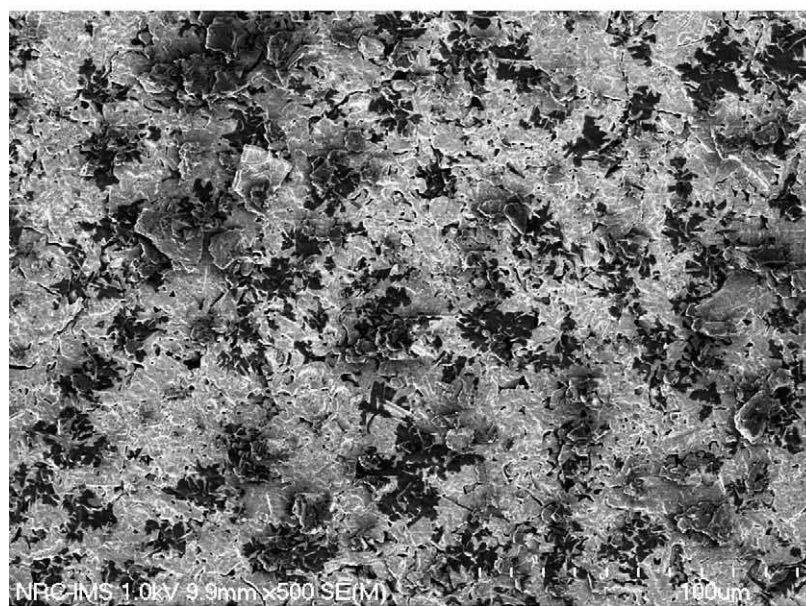

(b)

Fig. 3. Backscattered SEM images of (a) conventional and (b) microwave prepared  $\text{La}_2\text{Ni}_{0.9}\text{Co}_{0.1}\text{O}_{4+\delta}$  materials after firing at 1150 °C for 6 h.

signals the presence of a structural distortion [11]. It also shows an increase in  $a + b$  with cobalt content,  $x$ , whereas the  $c$ -parameter decreased sharply for the air-prepared samples,  $x = 0.00$ – $0.20$ , followed by a steady increase for the argon-prepared samples,  $x = 0.30$ – $1.00$ . This data, together with the dependence on  $\delta$  [8], suggests the  $c$ -parameter is strongly coupled to the electronic state of the cobalt ions. Structural refinements by Rietveld analysis of the powder neutron diffraction data were carried out with the interstitial defect models proposed earlier [3,4]. Whilst the distribution of oxygen across the sites was allowed to refine, the total oxygen contents were constrained to the values obtained by iodometric titration for all the refinements. The neutron data indicated that  $x = 0.50$  was still tetragonal  $F4/mmm$ , but  $x = 0.60$  has transformed to the orthorhombic  $Bmab$  cell. The refined structural parameters for these two compositions are shown in Table 1. Typical  $R_{wp}$  residuals for all compositions in the series were in the range of  $\sim 3.7$ – $5.7\%$ .

The sintering behaviour of the materials after firing for 6 h both conventionally and using microwaves were significantly different, as shown by the SEM images in Fig. 3. It is clear that the microwave-prepared materials were more porous than the conventionally prepared samples. It is thought that the more porous nature of the microwave-prepared sample is the cause of the improved ASR results for the microwave-prepared materials on CGO, see Fig. 4. The smaller variation in the ASR values observed with LSGM shows relative insensitivity to the type of firing method used. This can be explained by the fact that the Ruddlesden–Popper structure is structurally more closely matched to that of LSGM having a basic perovskite unit as compared to CGO, which has the antiferroite structure. Increasing the firing time in the microwave furnace to 12 h, yielded a material with similar porosity to the sample fired for 6 h in a conventional furnace.

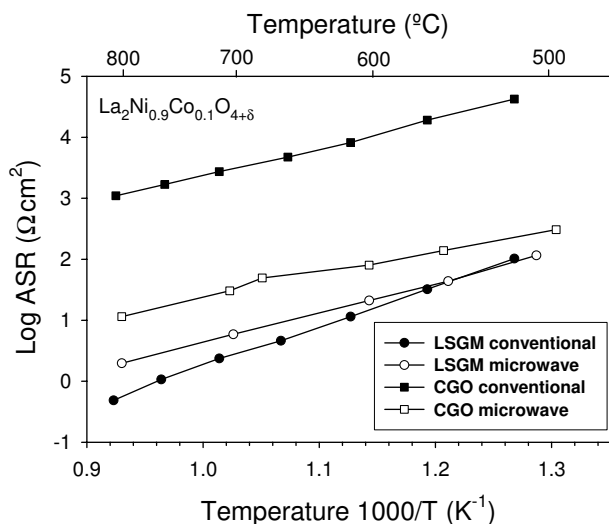


Fig. 4. Comparison of ASR data for  $\text{La}_2\text{Ni}_{0.9}\text{Co}_{0.1}\text{O}_{4+\delta}$  cathodes prepared by conventional and microwave methods.

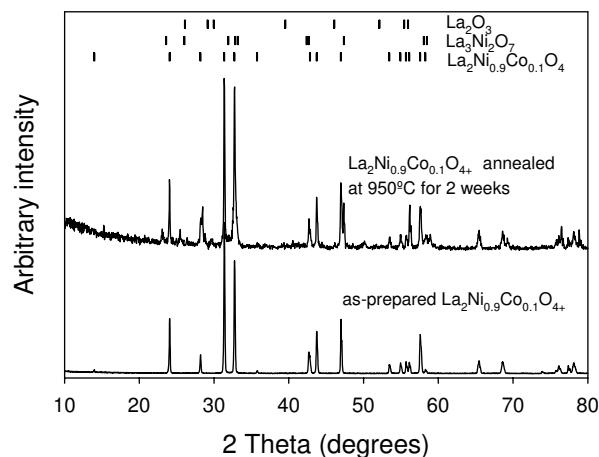


Fig. 5. X-ray diffraction pattern of as-prepared  $\text{La}_2\text{Ni}_{0.9}\text{Co}_{0.1}\text{O}_{4+\delta}$  and after firing at  $950^\circ\text{C}$  in air for 2 weeks on CGO. The strong ( $>10\%$ ) lines for  $\text{La}_3\text{Ni}_2\text{O}_7$  (PDF card 82-1934), and  $\text{La}_2\text{O}_3$  (PDF card 5-602), together with refined positions for as-prepared  $\text{La}_2\text{Ni}_{0.9}\text{Co}_{0.1}\text{O}_{4+\delta}$  are also indicated.

The long-term stability of  $\text{La}_2\text{Ni}_{0.9}\text{Co}_{0.1}\text{O}_{4+\delta}$  on both CGO and LSGM was tested by extended firing at  $950^\circ\text{C}$  in air. Fig. 5 shows the X-ray diffraction pattern of  $\text{La}_2\text{Ni}_{0.9}\text{Co}_{0.1}\text{O}_{4+\delta}$  after firing at  $950^\circ\text{C}$  for 2 weeks on CGO compared to the as-prepared powder. It can be seen that extensive decomposition has occurred. Decomposition products include oxidised lanthanum nickelates such as  $\text{La}_3\text{Ni}_2\text{O}_7$ . The same behaviour was observed for the electrodes deposited on LSGM. It is possible that the kinetics of the degradation reaction in the intermediate temperature SOFC range ( $<900^\circ\text{C}$ ) may be so slow that degradation would be negligible, but further study would be necessary to confirm this.

#### 4. Conclusions

The solid solution,  $\text{La}_2\text{Ni}_{1-x}\text{Co}_x\text{O}_{4+\delta}$ , has been successfully prepared by the Pechini method using both conventional and microwave heating. Successive substitution of cobalt for nickel in this series leads to a structural phase transition from tetragonal  $F4/mmm$  ( $x = 0$ – $0.50$ ) to orthorhombic  $Bmab$  ( $x = 0.60$ – $1.00$ ).

$\text{La}_2\text{Ni}_{1-x}\text{Co}_x\text{O}_{4+\delta}$ , where  $0.00 \leq x \leq 0.20$ , are stable in air, and therefore are potential candidates for SOFC cathode materials. Experiments have shown that microwave preparation of  $\text{La}_2\text{Ni}_{0.9}\text{Co}_{0.1}\text{O}_{4+\delta}$  for 6 h leads to higher porosity than conventionally synthesised material. It is hypothesised that this is the reason for the markedly lower ASR on CGO electrolyte. The long-term stability of  $\text{La}_2\text{Ni}_{0.9}\text{Co}_{0.1}\text{O}_{4+\delta}$  and CGO and LSGM is questionable, given the formation of secondary phases on extended annealing at  $950^\circ\text{C}$ . However, the retention of the smaller grained microstructure formed by the microwave synthesis, means that microwave processing may have benefits for long-term per-

formance, and should be investigated further with other materials.

### Acknowledgements

The authors would like to thank the National Research Council of Canada and the British Council for financial support. Mr. Jeff Fraser of the Institute for Microstructural Sciences, Ottawa, is thanked for assistance with obtaining the SEM micrographs.

### References

- [1] S.J. Skinner, J.A. Kilner, Oxygen diffusion and surface exchange in  $\text{La}_{2-x}\text{Sr}_x\text{NiO}_{4+\delta}$ , *Solid State Ionics* 135 (2000) 709–712.
- [2] V.V. Vashook, H. Ullman, O.P. Olshevskaya, V.P. Kulik, V.E. Lukashovich, L.V. Kokhanovskii, Composition and electrical conductivity of some cobaltates of the type  $\text{La}_{2-x}\text{Sr}_x\text{CoO}_{4.5-x/2\pm\delta}$ , *Solid State Ionics* 138 (2000) 99–104.
- [3] J.D. Jorgensen, B. Dabrowski, S. Pei, D.R. Richards, D.G. Hinks, Structure of the interstitial oxygen defect in  $\text{La}_2\text{NiO}_{4+\delta}$ , *Phys. Rev. B* 40 (1989) 2187–2199.
- [4] D.E. Rice, D.J. Buttrey, An X-ray diffraction study of the oxygen content phase diagram of  $\text{La}_2\text{NiO}_{4+\delta}$ , *J. Solid State Chem.* 105 (1993) 197–210.
- [5] P.S. Whitfield, I.J. Davidson, Microwave synthesis of  $\text{Li}_{1.025}\text{Mn}_{1.975}\text{O}_4$  and  $\text{Li}_{1+x}\text{Mn}_{2-x}\text{O}_{4-y}\text{F}_y$  ( $x = 0.05, 0.15$   $y = 0.05, 0.1$ ), *J. Electrochem. Soc.* 147 (2000) 4476–4484.
- [6] S.J. Skinner, C.N. Munnings, G. Amow, P.S. Whitfield, I.J. Davidson, Evaluation of  $\text{La}_2\text{Ni}_{1-x}\text{Co}_x\text{O}_{4\pm\delta}$  as a SOFC cathode material, in: S.C. Singhal, M. Dokiya (Eds.), *Solid Oxide Fuel Cells*, vol. VIII (PV2003-07), Electrochemical Society Inc., Pennington, NJ, USA, 2003, pp. 552–560.
- [7] P.A. Lessing, Mixed-cation oxide powders via polymeric precursors, *Am. Ceram. Soc. Bull.* 68 (1989) 1002–1007.
- [8] G. Amow, P.S. Whitfield, I.J. Davidson, R.P. Hammond, C.N. Munnings, S.J. Skinner, Structural and physical property trends of the hyperstoichiometric series,  $\text{La}_2\text{Ni}_{(1-x)}\text{Co}_x\text{O}_{4+\delta}$ , in: M.A. Alario-Franco, M. Greenblatt, G. Rohrer, M.S. Whittingham (Eds.), *Solid State Chemistry of Inorganic Materials IV*, MRS Proceeding, vol. 755, Materials Research Society, Warrendale, PA, USA, 2003, pp. 347–352.
- [9] Bruker AXS, TOPAS V2.1: general profile and structure analysis software for powder diffraction data, User Manual, Bruker AXS, Karlsruhe, Germany, 2003.
- [10] A.C. Larson, R.B. Von Dreele, *General Structure Analysis System*, LAUR 86-748, Los Alamos National Laboratory, 1994.
- [11] J.M. Longo, P.M. Raccach, The structure of  $\text{La}_2\text{CuO}_4$  and  $\text{LaSrVO}_4$ , *J. Solid State Chem.* 6 (1973) 526–531.